

A strategy based on water soluble coal tar pitches to construct MnO₂@C composite materials with high electrochemical performance

LIU Bo¹, WANG Kun^{1,4*}, GUO ZhaoQi¹, HAN BeiBei^{2,6}, XU GuiYing^{1*}, JU DongYing^{2,5}, AN BaiGang¹, LI YongCheng³, NI ZhenYong³ & ZHOU WeiMin^{1*}

¹ Key Laboratory of Energy Materials and Electrochemistry Research Liaoning Province, University of Science and Technology Liaoning, Anshan 114051, China;

² Advanced Science Research Laboratory, Saitama Institute of Technology, Fusaiji 1690, Japan;

³ Liaoning Starry Sky Sodium Battery Co., Ltd., Anshan 114051, China;

⁴ Sinosteel Anshan Research Institute of Thermo-Energy Co., Ltd., Anshan 114051, China;

⁵ State Key Laboratory of Marine Resource Utilization in South China Sea, Hainan Provincial Key Lab of Fine Chemistry, School of Chemical Engineering and Technology, Hainan University, Haikou 570228, China;

⁶ Key Laboratory of Advanced Fuel Cells and Electrolyzers Technology of Zhejiang Province, Ningbo Institute of Materials Technology and Engineering, Chinese Academy of Sciences, Ningbo 315201, China

Received November 16, 2022; accepted February 6, 2023; published online December 13, 2023

The water soluble coal tar pitches (WS-CTPs) were successfully prepared and used to construct the MnO₂@C composite materials by a hydrothermal method. It is interestingly observed that the structures and morphologies of MnO₂@C materials can be controlled by controlling the dosages of WS-CTPs and KMnO₄. Meanwhile, it is aware that MnO₂ exists in the MnO₂@C materials in an amorphous state. Compared with MnO₂, MnO₂@C materials output a remarkable improvement in electrochemical performance. For instance, MnO₂@C-0.3 shows the storage capacity at 965.7 mA h g⁻¹ after 300 cycles at a current density of 0.1 A g⁻¹. In addition, after 600 cycles at a current density of 1.0 A g⁻¹, the storage capacity of MnO₂@C-0.3 still keeps 450.3 mA h g⁻¹, indicating that MnO₂@C-0.3 owns tremendous cycle stability at a high current density. In view of the fact that the coal tar pitches possess great cost advantages, the strategy of using WS-CTPs as a carbon source to cover the metal oxides is a competitive way to expand the application of metal oxides in the fabrication of electrodes of LIBs.

water soluble coal tar pitches, MnO₂, composite materials, lithium ion batteries (LIBs), energy storage systems (ESSs), coal tar pitches

Citation: Liu B, Wang K, Guo Z Q, et al. A strategy based on water soluble coal tar pitches to construct MnO₂@C composite materials with high electrochemical performance. *Sci China Tech Sci*, 2023, 66, <https://doi.org/10.1007/s11431-022-2335-8>

1 Introduction

Nowadays, the green energy sources have received attention from numerous nations worldwide as a means of reducing

carbon emissions. Accelerating the development of energy storage systems (ESSs) is quickly becoming an effective countermeasure to store the energies which are produced by solar and wind energies. Lithium-ion batteries (LIBs) are a better choice for developing the ESSs due to their high energy density and long cycle life. Nevertheless, the low storage capacity of graphites is not satisfactory for the growing

*Corresponding authors (email: ustl15542731203@163.com; xuguiying751107@163.com; aszhou15242870697@163.com)

demands to develop ESSs [1–3].

As an alternative, a lot of research groups embark on the studies of metal oxides because they have extremely high storage capacity [4–7]. Among them, MnO_2 has been given a lot of attention because they possess the advantages such as high theoretical capacity (1230 mA h g^{-1}) and abundant resources [8,9]. Zhang et al. [10] successfully prepared the nano MnO_2 with high crystallinity and revealed it shows the significantly high storage capacity (1095 mA h g^{-1}) at 0.1 A g^{-1} . However, the large volume change generated during the storage of Li^+ facily causes the collapse of the crystal, which results in the reduction of the long cycle performance of MnO_2 . Meanwhile, the poor conductivity of MnO_2 easily leads to the production of polarization, and further decreases its rate performance [11,12].

It is well known that covering the carbon materials on the surface of MnO_2 is an effective way to solve the aforementioned problems. This method not only provides a possible solution to restrict the lattice expansion problem, but also provides an excellent conductive network for metal oxides, improving storage capacity [13,14]. Up to now, platy of carbon sources such as graphene and carbon nanotubes are widely used to cover the metal oxides [15–17]. However, the complex fabrication process and extremely high fabrication costs restrict the actual applications of these carbon sources. Coal tar pitches based carbons are coming into view of researchers because they have the contents of polycyclic aromatic hydrocarbons (PAHs) so that the carbons prepared by coal tar pitches exhibit the significantly excellent conductivity and cost advantage [18,19]. Zeng et al. [14] used coal tar pitches as carbon sources and a template method to construct carbon substrates, the MnO_2/PGC composite materials were synthesized based on the fabricated carbon substrates and *in situ* precipitation method. Wang et al. [4] fabricated the metal oxide/carbon composite materials by directly mixing the coal tar pitches with the metal oxides. Nevertheless, these methods can not completely address issues such as agglomeration among the metal oxide particles and control of the sizes of metal oxides.

To address the aforementioned problems, the water soluble coal tar pitches (WS-CTPs) were prepared and used as the covering materials. The WS-CTPs possess the characteristics of good water solubility and contain a lot of PAHs, causing that the WS-CTPs are able to become excellent carbon sources for fabricating the metal oxides/carbon composite materials. Thus, based on the usage of a hydrothermal method, the novel WS-CTPs based $\text{MnO}_2@\text{C}$ materials were successfully synthesized by using the KMnO_4 and WS-CTPs. It is interestingly found that MnO_2 exists in the $\text{MnO}_2@\text{C}$ materials in the amorphous state, and the $\text{MnO}_2@\text{C}$ composite materials manifest different structures with conversing the dosages of WS-CTPs.

After detailed electrochemical investigations, it is ob-

served that the $\text{MnO}_2@\text{C}$ materials exhibit the fabulous storage capacity. It is noteworthy that a lot of defects on amorphous MnO_2 provided the active sites for storing Li^+ , leading to the enhancement of storage capacity. Considering the fact that coal tar pitches are industrial commodities, the WS-CTPs based $\text{MnO}_2@\text{C}$ materials exhibit significant cost advantages in the fabrication of EES.

2 Experimental

2.1 Characterization

The AVATAR 360 infrared spectrometer (FT-IR) was used to analyze the functional groups on the surfaces of the samples. The X-ray diffraction (XRD) patterns were measured with an X'pert Powder instrument from PANalytical at 40.0 kV and 40 mA with $\text{Cu-K}\alpha$ radiation. The results of X-ray photoelectron spectroscopy (XPS) were verified by a K-Alpha instrument using an $\text{Al-K}\alpha$ source (12 kV) from Thermo Fisher Scientific, USA. The structures of the samples were analyzed by the HR 800 laser Raman spectrometer of Horiba Jobin Yvon company, France. Nitrogen adsorption and desorption isotherms were measured by a Quadasorb autosorb-iQ surface analyzer which was purchased from Quantachrome Instruments, USA. The specific surface area was evaluated, according to the Brunauer-Emmett-Teller (BET) method. Based on a DFT model the size distributions were evaluated. Morphological features were described by scanning electron microscopy (SEM) using an instrument produced by Carl Zeiss AG, Germany. TEM measurements were performed on the HF-3300 system (Hitachi Co. Ltd., Tokyo, Japan). Thermogravimetry (TG) measurements were recorded using a Rigaku TG-DTA8122 thermal analyzer under a flow of air with a heating rate of $10^\circ\text{C}/\text{min}$. Cyclic voltammetry (CV) and electrochemical impedance spectroscopy (over a frequency range of 100 kHz – 0.01 Hz and the amplitude was 5 mV) were tested by CHI660E electrochemical workstation (ChenHua, Shanghai, China).

2.2 Preparations of water soluble coal tar pitch based carbons (WS-CTPCs)

The coal tar pitch (5 g) was added in a mortar and ground in size which is less than $45 \mu\text{m}$. Then, the sulfuric acid (95 wt%–98 wt%, 70 mL) and nitric acid (65 wt%–68 wt%, 30 mL) were added to a round-bottom flask, and then this acid mixture was stirred for 5 h at 40°C . After the reaction, the mixture was filtered, and the obtained solids were washed by de-ionized water until the pH value of washed solution became neutral. The obtained solids were mixed with NaOH (1 mol L^{-1}) until the pH value of the obtained mixture was over 12, and then this mixture was continuously stirred for 1 h at 80°C . Thereafter, the HCl (1 mol L^{-1}) was added to the

same mixture until its pH value was smaller than 2. At the same time, it was observed that black solids formed in this mixture. The solids were obtained by centrifugal separation and then placed in a drying oven for 12 h at 80°C. Finally, the obtained solids were named as water soluble coal tar pitches (WS-CTPs), and placed in a tube furnace for 5 h at 400°C in N₂ atmosphere. The obtained carbons that are processed with carbonization were named WS-CTPCs.

2.3 Preparation of CTPs based MnO₂@C composite materials

The KMnO₄ (0.5 g), H₂SO₄ (0.3 mL) and deionized water (15 mL) were mixed, and then this mixture was named as α solution. WS-CTPs were dissolved in the deionized water (20 mL), and the 1 mol L⁻¹ NaOH was dropped into the solutions containing WS-CTPs until its pH value became 10. The solution containing WS-CTPs was named β solution. The β solution was mixed with α solution, and then the obtained mixture was stirred uniformly. This mixture was placed in a high-pressure reactor for 6 h at 150°C. After cooling down to the room temperature, this mixture was filtered, and the obtained solids were placed in a drying oven for 12 h at 80°C. Finally, the obtained solids were placed in a tube furnace for 5 h at 400°C in N₂ atmosphere. According to the adding amount of WS-CTPs (0.3, 0.4 and 0.5 g), the obtained MnO₂@C composite materials were named as MnO₂@C-X (X = 0.3, 0.4 and 0.5), respectively. Nevertheless, the solids did not form when a dosage of WS-CTPs was set at 0.2 g.

2.4 Electrochemical measurements

The electrochemical cells were assembled by using the MnO₂@C composite materials. The MnO₂@C composite materials (0.08 g) were respectively mixed with acetylene black (0.015 g) and polyvinylidene fluoride (PVDF) binder (0.005 g) in a weight ratio of 80:15:5 in *N*-methyl-2-pyrrolidone (NMP) solution. The fabricated slurry was coated on

the Cu foil and dried in a vacuum drying oven at 80°C for 1 h so as to remove the solution. Continuously, the Cu foil with the active materials was dried at 120°C for 12 h, and cut into round shape strips of φ 11 mm. The mass loading of the active materials was at 1.20 mg/cm². The two-electrode electrochemical cells (CR2032 coin-type) were assembled in a glove box filled with high-purity argon. The lithium metal foil (φ 15.60 mm \times 0.45 mm) was a reference electrode. Celgard 2400 micro-porous membrane was a separator, and 1 mol L⁻¹ LiPF₆ in the mixture of EC, DMC, EMC (1:1:1, vol%) was an electrolyte. Galvanostatic charge-discharge tests were conducted by LAND (CT 2001A) battery test system at a 0.01–3.00 V. CV and electrochemical impedance spectroscopy (EIS) measurements were performed by using the CHI 660E. The CV curves were recorded in a voltage region of 0.01–3.00 V at a scan rate of 0.2 mV/s. The impedance spectra were recorded in a frequency range of 100 kHz–0.01 Hz.

3 Results and discussion

The synthesis procedures of MnO₂@C-0.3 material are described in Figure 1. The carbon contents in MnO₂@C materials were first determined by TGA measurements (Figure S1). The slight mass loss occurring below 200°C is generally attributed to the loss of water. The significant weight losses were observed at a temperature range of 350°C–500°C, which was ascribed to the burning of carbons of MnO₂@C materials. When the temperature was increased to 550°C, the weight loss became negligible [20,21]. After calculations, the carbon contents of MnO₂@C-0.3, MnO₂@C-0.4 and MnO₂@C-0.5 were 34%, 45%, and 53%, respectively.

In the comparison with the CTPs, the conversions of groups on WS-CTPs were verified by FT-IR measurements. It was distinct that novel peaks of 1045, 1345, 1530 and 1720 cm⁻¹ corresponding to the –C–O, –C–OH, –NO₂ and –C=O groups appeared in the WS-CTPs (Figure S2(a)) [22–24]. Meanwhile, the intensity of 3420 cm⁻¹ attributing to

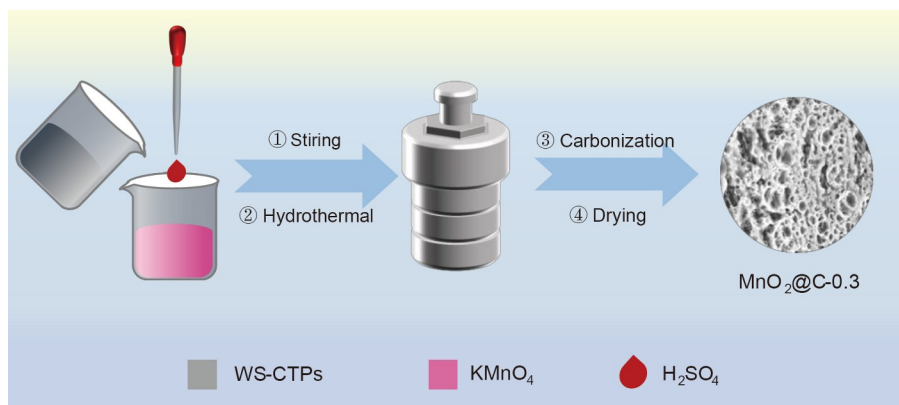


Figure 1 (Color online) Synthesis procedures of MnO₂@C-0.3 material.

the –OH group increased in the WS-CTPs. The existences of hydrophilic functional groups cause that WS-CTPs are able to dissolve in water (Figure S2(b)). Zhang et al. [25] indicated that the oxygen functional groups on the surface of carbon materials can help to increase the dispersion ability of carbon materials and the adsorption ability for metal ions, leading to the excellent dispersion of nano-sized metal oxide. Likewise, it is also considerable that nano MnO_2 can be dispersed in carbon substrates very well.

To inquire into the chemical states of $\text{MnO}_2@C$ materials, the XPS measurements were performed in detail. As shown in Figure 2(a), the binding energies of Mn $2p_{1/2}$ and Mn $2p_{3/2}$ were observed at 653.0 and 641.2 eV, respectively. Especially, the differences between the binding energies are 11.8 eV, which corresponds to a feature of MnO_2 [26]. After fitting the two peaks of Mn $2p_{1/2}$ and Mn $2p_{3/2}$, the mixed oxidation states of Mn^{4+} and Mn^{3+} were observed at 655.0, 643.4 eV (Mn^{4+}) and 653.2, 641.4 eV (Mn^{3+}), respectively [27]. At the present stage, the existence of Mn^{3+} demonstrates the abundant structural defects nature, which probably plays a role to facilitate the formation of the amorphous state [28,29]. The peak of N 1s was able to be fitted to the ~ 398.5 eV (N-6) and ~ 400.0 eV (N-5), respectively, indicating that N elements of WS-CTPs exist in $\text{MnO}_2@C$ as N-6 and N-5 types, which can facilitate the infiltration and charge transfer, leading to the improvement of storage ca-

capacity [30,31] (Figure 2(b)). In addition, the N contents in $\text{MnO}_2@C$ materials were calculated as 3.81 at%, 5.18 at% and 6.47 at%, respectively, revealing that N contents slightly increase with increasing the dosages of water soluble pitches (Figure S3).

The structure of MnO_2 in $\text{MnO}_2@C$ materials was verified by the XRD measurements (Figure 3(a)). Similar to the synthesis process of $\text{MnO}_2@C$, the MnO_2 was also synthesized in our studies. In accordance with the standard card (ICOD No.00-044-0141), it was aware that prepared MnO_2 only exhibited the tetragonal structure [32]. Nevertheless, the analogous structure was not observed in the $\text{MnO}_2@C$ entirely, indicating that MnO_2 existed in $\text{MnO}_2@C$ composite materials as an amorphous state. It is thought that the additions of WS-CTPs prevent the growth of crystal lattices, causing the MnO_2 of $\text{MnO}_2@C$ composite materials to be in an amorphous state. On the other hand, the peak of 25° attributing to the (002) increased with increasing the dosages of WS-CTPs, revealing that carbon contents in $\text{MnO}_2@C$ increased with the increasing the additional dosages of WS-CTPs (Figure 3(a)).

The structures of MnO_2 and $\text{MnO}_2@C$ materials were also verified by Raman measurements (Figure 3(b)). Similar to the general carbon materials, the *D* and *G* peaks were observed at 1357.5 and 1587.3 cm^{-1} , respectively. In addition, the intensity of *D* is obviously stronger than *G*, indicating

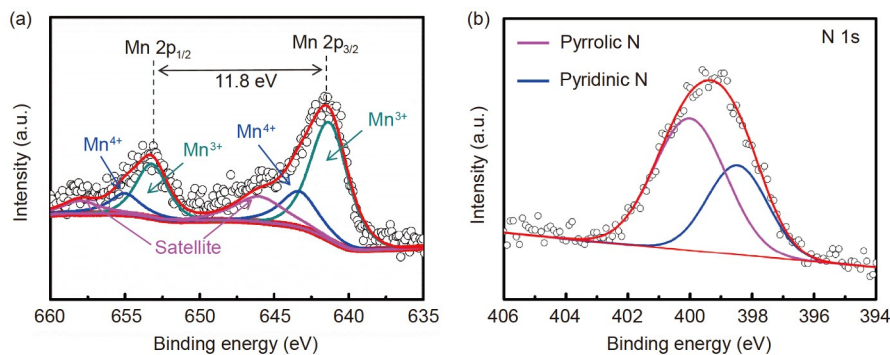


Figure 2 (Color online) XPS fitting results of Mn $2p_{1/2}$ and Mn $2p_{3/2}$ (a) and N 1s (b) of $\text{MnO}_2@C-0.3$ material.

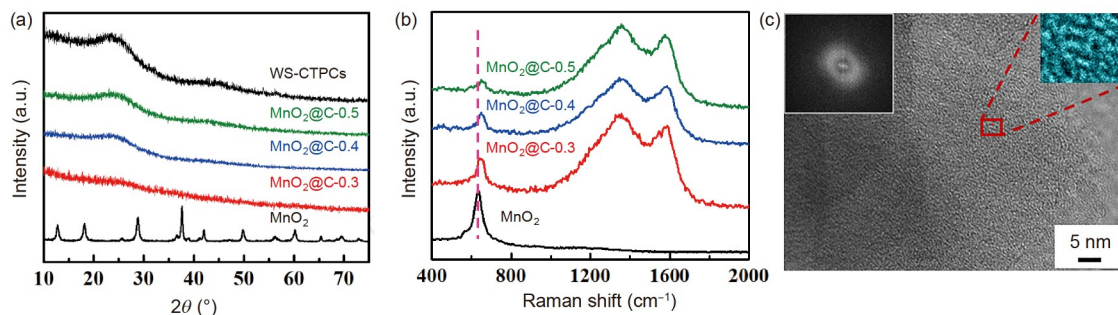


Figure 3 (Color online) (a) XRD pattern of MnO_2 , WS-CTPs and $\text{MnO}_2@C$ materials; (b) Raman spectra of MnO_2 , WS-CTPs and $\text{MnO}_2@C$ materials; (c) TEM image of $\text{MnO}_2@C-0.3$ material.

that carbons in $\text{MnO}_2@\text{C}$ are in the amorphous state [24,33]. Compared with the MnO_2 , the characteristic peak of Mn–O (648.9 cm^{-1}) slightly shifted to the right and then became broad in the $\text{MnO}_2@\text{C}$ materials, which suggests that the MnO_2 of the $\text{MnO}_2@\text{C}$ materials is in the amorphous state [34,35].

In the TEM image, the long-range ordered structures were not observed in the $\text{MnO}_2@\text{C}$ materials, which was indicative that the MnO_2 and carbons in the $\text{MnO}_2@\text{C}$ materials exist in an amorphous state. The corresponding fast Fourier transform (FFT) image can further confirm the amorphous nature of $\text{MnO}_2@\text{C}$ materials (Figure 3(c)). Additionally, it was different from the characteristic inter-lamellar spacing (0.363 nm) of carbons, an observation of lattice fringes with an interplane distance of 0.690 nm is probably attributed to the MnO_2 [17,29,36]. These aforementioned XPS, XRD, Raman and TEM measurements furnish convincing proof that MnO_2 compounds exist in the $\text{MnO}_2@\text{C}$ composite materials as an amorphous state.

The morphologies of MnO_2 and $\text{MnO}_2@\text{C}$ materials were described in (Figure 4(a)–(c)). Firstly, the synthesized MnO_2 is constructed by the nano-sized fibers with a width of $\sim 48\text{ nm}$, as shown in Figure S4. By contrast, it is obvious that the morphologies of MnO_2 exceedingly changed in $\text{MnO}_2@\text{C}$ materials (Figure 4(a)–(c)). One possible explanation for this may be the hydrophilic functional groups in WS-CTPs break the formation of MnO_2 crystals. It is noteworthy that $\text{MnO}_2@\text{C}-0.3$ shows the well-developed and cross-linked pore structures, which facilitate the infiltration of electrolyte to improve the charge transfer [37,38]. Additionally, SEM-EDX mapping indicates that C, O, Mn and N elements dispersed homogeneously (Figure

S5). With increasing the dosages of WS-CTPs, it was observed that a lot of spherical particles fused to each other, leading to the formations of rodlike structures in $\text{MnO}_2@\text{C}-0.4$ material. Furthermore, the $\text{MnO}_2@\text{C}-0.5$ approximately was the uneven block structure, which implies the poor dispersion between each component of metal oxide@C composites. The noticeable conversions of morphologies are likely caused to the increase of hydrogen bonds between the $-\text{COOH}$ and $-\text{OH}$ groups of WS-CTPs in reactive cases, with increasing the addition amount of WS-CTPs. These hydrogen bond interactions among the coal tar pitches can decrease the thermal decompositions of coal tar pitches, decreasing the formation of complex porous structures. Meanwhile, the hydrogen bond interactions also decrease the dispersion of MnO_2 in $\text{MnO}_2@\text{C}$ materials, which is able to decrease the formations of complex porous structures [39].

The nitrogen adsorption experiment was performed to examine the pore characteristics of $\text{MnO}_2@\text{C}$ materials (Figure S6). After calculations, the specific surface areas of MnO_2 , $\text{MnO}_2@\text{C}-0.3$, $\text{MnO}_2@\text{C}-0.4$ and $\text{MnO}_2@\text{C}-0.5$ were 45.2 , 84.7 , 362.4 and $290.7\text{ m}^2\text{ g}^{-1}$, respectively (Table S1). Compared with the $\text{MnO}_2@\text{C}-0.4$ and $\text{MnO}_2@\text{C}-0.5$, the $\text{MnO}_2@\text{C}-0.3$ owned extremely complex porous structures (Figure 4(d)). In particular, the existences of numerous mesoporous in $\text{MnO}_2@\text{C}-0.3$ are able to provide a tremendous transmission channel for Li^+ ions, causing the chemical kinetics of $\text{MnO}_2@\text{C}-0.3$ to increase remarkably [40–43].

On the basis of evaluations for structures of $\text{MnO}_2@\text{C}$ materials, their electrochemical performance was synthetically investigated. In the cycling performance, the MnO_2 only showed the storage capacity at 60 mA h g^{-1} after 100 cycles. By contrary, the $\text{MnO}_2@\text{C}-0.3$, $\text{MnO}_2@\text{C}-0.4$ and

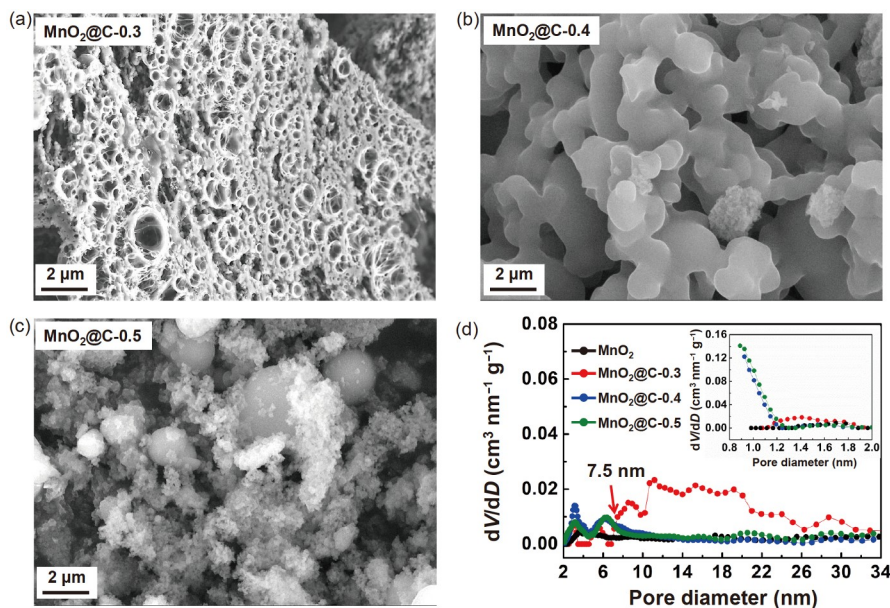


Figure 4 (Color online) (a)–(c) SEM morphologies of $\text{MnO}_2@\text{C}$ materials; (d) pore size distribution curves of MnO_2 and $\text{MnO}_2@\text{C}$ materials.

MnO₂@C-0.5 exhibited the storage capacity at 865.2, 647.2 and 420.9 mA h g⁻¹ after 100 cycles, respectively. These results indicate that covering carbon materials on the surface of MnO₂ is an efficacious way to enhance the actual storage capacity of MnO₂ (Figure 5(a)). Meanwhile, the formation of MnO₂ in the amorphous state is also beneficial to prevent the breaking of structures in the repeated Li insertion-extraction process, enhancing the storage capacity and cycling stability [44–46]. Similar to the general metal oxides such as MnO_x, Fe₂O₃ and Co₃O₄, the trend from decline to rise in cycling performance is also obviously observed in MnO₂@C-0.3. Likewise, with the proceeding of the charge-discharge process, the breaking of SEI and then forming of a polymeric gel-like film cause an appearance of the above-mentioned phenomenon in the cycling performance of MnO₂@C-0.3 [30,47,48].

As shown in Figure 5(b), the MnO₂@C-0.3 manifested more tremendous rate performance than others. For instance, when the current densities were set at 0.1, 0.2, 0.5, 1.0, 2.0 and 5.0 A g⁻¹, the storage capacity of MnO₂@C-0.3 was 734.1, 586.8, 516.8, 428.2, 318.9 and 129.5 mA h g⁻¹, respectively. As shown in Figure 5(c)–(d), the long cycling stability of MnO₂@C-0.3 was also investigated. Surprisingly, after the initial decrease, the discharge capacity of MnO₂@C-0.3 gradually increases to 965.7 mA h g⁻¹ at 0.1 A g⁻¹ after 300 cycles. Furthermore, MnO₂@C-0.3 still

possesses an excellent capacity of 450.3 mA h g⁻¹ after 600 cycles, even at a higher current density of 1.0 A g⁻¹. As far as reversible capacity and rate performance are concerned, it is clear that the MnO₂@C-0.3 presents superior lithium storage performance compared with some previously reported manganese oxides (Table S2).

CV curves of MnO₂ and MnO₂@C materials were illustrated in Figures S7(a) and 6(a)–(c). As shown in Figure S7(a), two reductive peaks were observed at 1.8 and 1.0 V in the first cycle, respectively, which correspond to the reduction Mn⁴⁺ to Mn²⁺ (MnO₂+2Li⁺+2e⁻ → MnO+Li₂O) and the further reduction from Mn²⁺ to Mn⁰ (MnO+2Li⁺+2e⁻ → Mn+Li₂O), respectively [10]. The reductive peak at 0.1 V in the first cycle was generally attributed to the formation of solid electrolyte interphase (SEI) and side reactions between Li⁺ and active materials. In addition, the oxidative peak at 1.1 V was considered a result of a reaction of Mn⁰ to Mn²⁺ [14,16]. However, these reductive and oxidative peaks were rarely observed from the second cycle, which is possibly due to the breaking structures of MnO₂.

On the basis of analyses of MnO₂, the electrochemical characteristics of MnO₂@C-0.3 were performed in detail. The two reductive peaks (0.7 and 1.4 V) appear at the second cycle of MnO₂@C-0.3, corresponding to a two-step possible reduction process Mn^{3+/4+} to Mn²⁺, Mn²⁺ to Mn⁰ (Figure 6(a)). Two oxidative peaks located in 1.1 and 2.1 V could con-

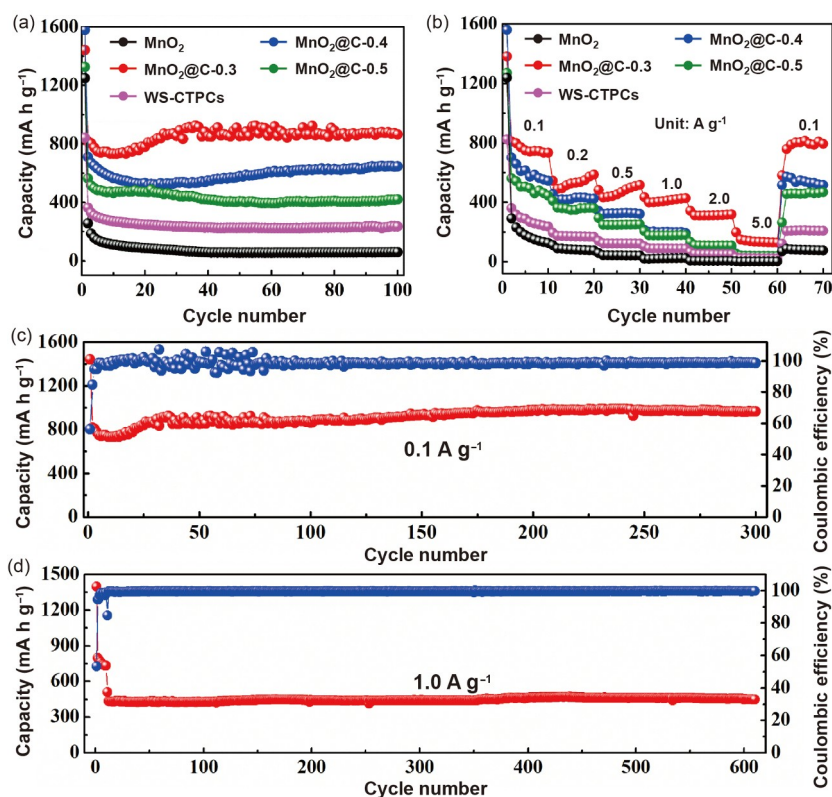


Figure 5 (Color online) (a) Cycling performance of WS-CTPCs, MnO₂ and MnO₂@C materials; (b) rate performance of WS-CTPCs, MnO₂ and MnO₂@C materials; (c) storage capacity of MnO₂@C-0.3 at 0.1 A g⁻¹ after 300 cycles; (d) storage capacity of MnO₂@C-0.3 at 1.0 A g⁻¹ after 600 cycles.

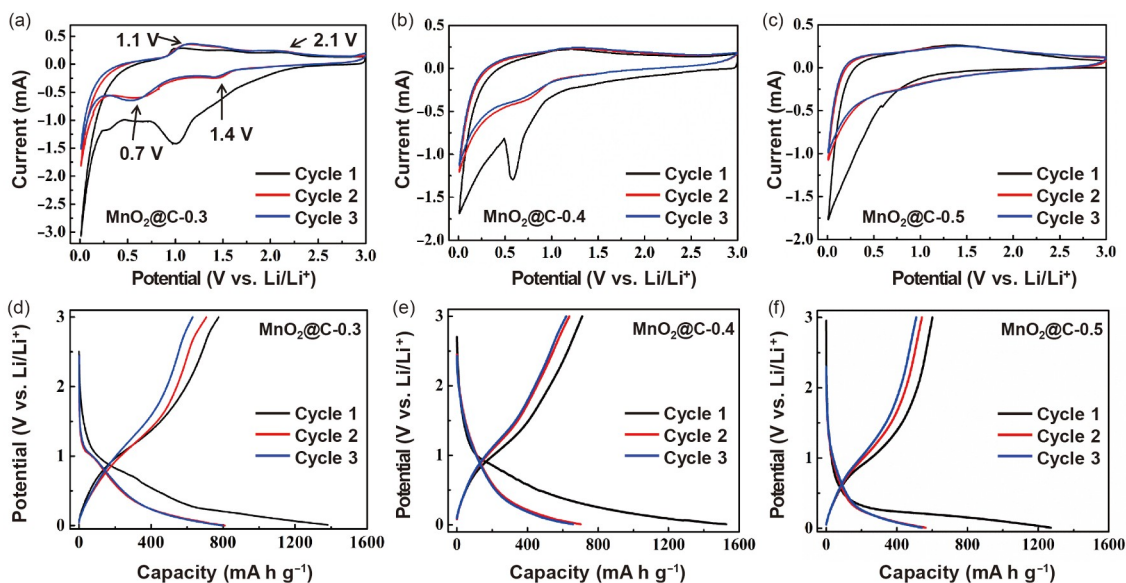


Figure 6 (Color online) (a)–(c) CV curves of $\text{MnO}_2@\text{C}$ materials; (d)–(f) charge-discharge profiles of $\text{MnO}_2@\text{C}$ materials.

ceivably be hypothesized that the reoxidation of manganese contains two steps, which demonstrates that the oxidation process of Mn to MnO_2 is a two-step reaction process [49]. Associated with the evaluative results of XRD, the slightly shifting left was probably attributed to that the MnO_2 of $\text{MnO}_2@\text{C}-0.3$ is in the amorphous state, leading to the conversions of CV measurement results of MnO_2 and $\text{MnO}_2@\text{C}-0.3$. In addition, it is different from the MnO_2 (Figure S7(a)), the four peaks still exist from the second cycle (Figure 6(a)), which is strongly suggestive that covering the carbon materials is the effective way to overcome the breaking of MnO_2 in the charge-discharge processes. However, the peaks were not observed obviously in the $\text{MnO}_2@\text{C}-0.4$ and $\text{MnO}_2@\text{C}-0.5$ materials, revealing the excess amount of WS-CTPs is not suitable for developing the electrochemical performance of MnO_2 (Figure 6(b)–(c)).

The electrochemical performance of MnO_2 and $\text{MnO}_2@\text{C}$ materials were further verified by the charge-discharge measurements (Figure 6(d)–(f)). The first coulombic efficiencies of $\text{MnO}_2@\text{C}-0.3$, $\text{MnO}_2@\text{C}-0.4$ and $\text{MnO}_2@\text{C}-0.5$ were 56.2%, 45.5% and 47.3%, respectively. Generally, the low first coulombic efficiencies are attributed to the formation of SEI and irreversible reactions between Li^+ and active materials. Compared with the MnO_2 (Figure S7(b)), it was observed that $\text{MnO}_2@\text{C}-0.3$ exhibited a sloping charge-discharge plateau, which is probably ascribed to the enhancement of pseudocapacitance effect [50,51]. By contrast, this sloping plateau was not observed in the $\text{MnO}_2@\text{C}-0.4$ and $\text{MnO}_2@\text{C}-0.5$ materials. On the basis of the aforementioned analyses, it can be assumed that dimensional hierarchical porous structures of $\text{MnO}_2@\text{C}-0.3$ are conducive to enhance its pseudocapacitance effect [49,52].

The charge transfer abilities of MnO_2 and $\text{MnO}_2@\text{C}$ materials were evaluated by electrochemical impedance spectroscopy (EIS) measurements (Figure 7). Figure 7(a) exhibited that $\text{MnO}_2@\text{C}-0.3$ possessed the smaller diameters of semicircle loop at high frequency region than MnO_2 and other $\text{MnO}_2@\text{C}$ materials, suggesting that $\text{MnO}_2@\text{C}-0.3$ showed a more excellent conductivity than the others. Additionally, according to Yang et al. [7] and Tai et al. [9], the R_{ct} values of $\text{MnO}_2@\text{C}-0.3$, $\text{MnO}_2@\text{C}-0.4$ and $\text{MnO}_2@\text{C}-0.5$ were calculated at 56.12, 68.08 and 263.90 Ω , respectively, revealing the $\text{MnO}_2@\text{C}-0.3$ owned more tremendous charge transfer properties. It is considerable that three dimensional hierarchical porous structures and excellent dispersions of MnO_2 in $\text{MnO}_2@\text{C}-0.3$ accelerate the Li^+ transfer so that the reaction kinetics of $\text{MnO}_2@\text{C}-0.3$ were improved remarkably [53].

In general, the σ value of the Warburg coefficient is used to evaluate the Li diffusion performance. The Randles plot plotting of Z' with $\omega^{-1/2}$ ($\omega = 2\pi f$) for a low-frequency is used to obtain σ values (Figure 7(b)). Namely, the larger σ value reflects the poor ion diffusion performance [54]. As a result, the σ values of $\text{MnO}_2@\text{C}-0.3$, $\text{MnO}_2@\text{C}-0.4$ and $\text{MnO}_2@\text{C}-0.5$ were respectively calculated as 65.5, 72.2 and 209.2 $\Omega/\text{s}^{1/2}$, indicating that the $\text{MnO}_2@\text{C}-0.3$ owned the exceedingly higher Li^+ diffusion performance than other $\text{MnO}_2@\text{C}$ materials. The excellent transfer ability of $\text{MnO}_2@\text{C}-0.3$ was attributed to its complicated structures. Therefore, it is thought that adjusting the dosages of WS-CTPs is an effective way to synthesize the $\text{MnO}_2@\text{C}$ composite materials having fabulous electrochemical performance.

In accordance with a report by Wang et al. [52], the storage

mechanism of $\text{MnO}_2@\text{C}-0.3$ was finally discussed. As shown in Figure 8(a), it was obviously found that the $\text{MnO}_2@\text{C}-0.3$ exhibited excellent electrochemical stability at different scan rates in a voltage range of (0.01–3.00 V). After detailed calculations, the fact that the capacitive effect occupied a relatively large proportion (64.0%) for a contribution of storing Li^+ was observed, which is higher than that of $\text{MnO}_2@\text{C}-0.4$ (60.7%) and $\text{MnO}_2@\text{C}-0.5$ (46.4%), respectively (Figure 8(d)–(f)). Because the specific surface area of $\text{MnO}_2@\text{C}-0.3$ is relatively small ($84.7 \text{ m}^2 \text{ g}^{-1}$), the main capacitive contribution could be considered as pseudocapacitance rather than double layer charging. In summary, the high pseudocapacitance contribution is ascribed to the rapid electron transfer. The existence of abundant structural defects in MnO_2 can reduce the energy barrier of charge transfer during the redox reaction, while the nitrogen and oxygen elements in the carbon contents serve as active sites to store lithium ions reversibly [53,55,56].

4 Conclusion

The WS-CTPs were prepared using coal tar pitches according to a mixing acid method. The $\text{MnO}_2@\text{C}$ composite materials were successfully synthesized by using the KMnO_4 and WS-CTPs. It is observed that complex porous structures of $\text{MnO}_2@\text{C}$ can be controlled by adjusting the addition amount of reactive materials of KMnO_4 and WS-CTPs. The complex porous structures and MnO_2 in the amorphous state enhanced the pseudocapacitance of $\text{MnO}_2@\text{C}$ materials, leading to remarkable improvement in their storage capacity. As an example, the storage capacity $\text{MnO}_2@\text{C}-0.3$ is $965.7 \text{ mA h g}^{-1}$ after 300 cycles at a current density of 0.1 A g^{-1} . When the current density was set at 1.0 A g^{-1} , the $\text{MnO}_2@\text{C}-0.3$ still exhibits the storage capacity at $450.3 \text{ mA h g}^{-1}$ after 600 cycles. In light of the fact that the coal tar pitches possess the cost-effective advantage, we will consider that the method using WS-CTPs as a carbon source

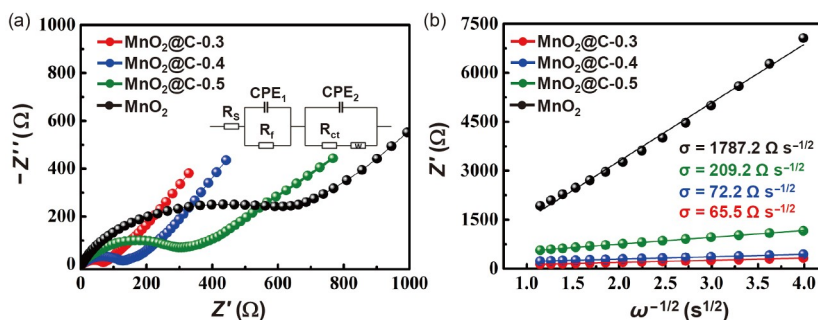


Figure 7 (Color online) Nyquist plot results (a) and illustrations of relationships between Z' and $\omega^{-1/2}$ in the low-frequency region (b). Among them, R_s represents the resistances associated with solution, wires, and contacts. R_f and CPE_1 (constant phase element) represent the Faradaic and non-Faradaic pathways of the SEI layer, respectively. R_{ct} is the charge transfer resistance, together with another CPE_2 , represents the charge transfer reaction. The Warburg element W stands for the diffusion kinetics of the Li ion through the electrode materials.

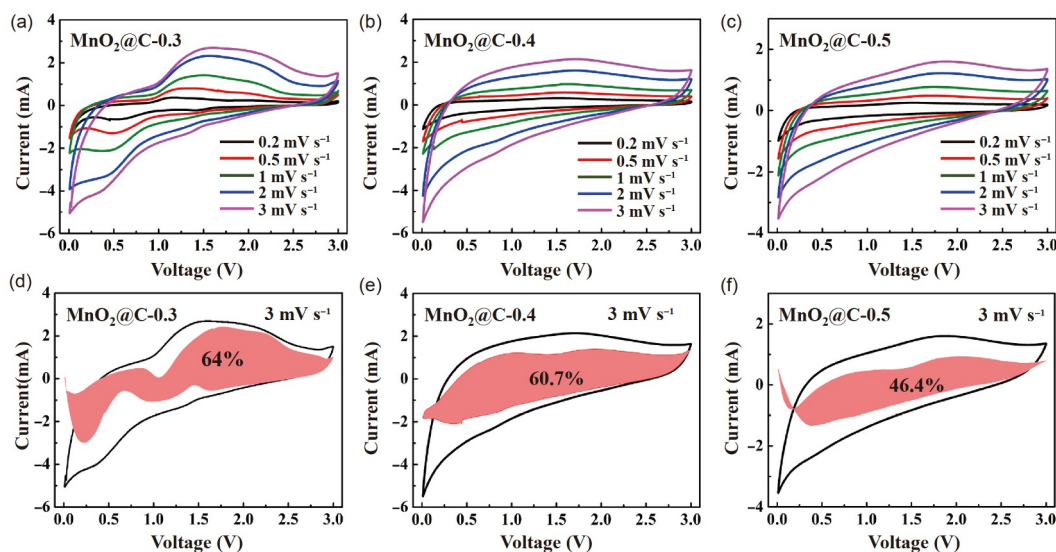


Figure 8 (Color online) (a)–(c) CV curves of $\text{MnO}_2@\text{C}$ materials at different scan rates. (d)–(f) Capacitive contributions of $\text{MnO}_2@\text{C}$ materials at a scan rate of 3 mV s^{-1} .

is a significantly favorable way to expand actual applications of metal oxides in fabrications of electrode materials of LIBs.

This work was supported by the University of Science and Technology Liaoning (Grant Nos. 601009816-39 and 2017RC03), the Liaoning Province Education Department of China (Grant Nos. 601009887-16 and LJKQZ2021126), the National Natural Science Foundation of China (Grant Nos. 51672117 and 51672118), and the Postdoctoral Foundation Project of Shenzhen Polytechnic (Grant No. 6020330007K).

Supporting Information

The supporting information is available online at tech.scichina.com and link.springer.com. The supporting materials are published as submitted, without typesetting or editing. The responsibility for scientific accuracy and content remains entirely with the authors

- Huang Y, Tang Y, Yuan W, et al. Challenges and recent progress in thermal management with heat pipes for lithium-ion power batteries in electric vehicles. *Sci China Tech Sci*, 2021, 64: 919–956
- Li J, Xu G, Wang K, et al. Study on fabrication and electrochemical performances of Fe₇S₈@C composite materials. *Electrochemistry*, 2020, 88: 380–386
- Wang K, Ju D, Xu G, et al. Enhanced Li ion storage performances of carbon black by introducing organosulfur groups on surface. *Electrochemistry*, 2020, 88: 8–13
- Wang K, Ju D, Xu G, et al. Study on electrochemical performances of composite carbon (FeO/C) materials fabricated by coal tar pitch and Fe₃O₄ particles. *Int J Hydrogen Energy*, 2019, 44: 25199–25206
- Wang L, Nie Z, Cao C, et al. Carbon-wrapped TiO₂ nanocubes exposed with (001) active facets for high-rate and long-life lithium-ion batteries. *J Power Sources*, 2016, 302: 259–265
- Zhang J, Zhu Y, Cao C, et al. Microwave-assisted and large-scale synthesis of SnO₂/carbon-nanotube hybrids with high lithium storage capacity. *RSC Adv*, 2015, 5: 58568–58573
- Yang L, Wu Y, Wu Y, et al. Hierarchical flower-like Fe₂O₃ mesoporous nanosheets with superior electrochemical lithium storage performance. *J Energy Storage*, 2019, 23: 363–370
- Khalid S, Cao C, Naveed M, et al. 3D hierarchical MnO₂ microspheres: A prospective material for high performance supercapacitors and lithium-ion batteries. *Sustain Energy Fuels*, 2017, 1: 1795–1804
- Tai Z, Shi M, Zhu W, et al. Carbon-coated β-MnO₂ for cathode of lithium-ion battery. *Sustain Energy Fuels*, 2020, 4: 1704–1711
- Zhang L, Song J, Liu Y, et al. Tailoring nanostructured MnO₂ as anodes for lithium ion batteries with high reversible capacity and initial coulombic efficiency. *J Power Sources*, 2018, 379: 68–73
- Meng Y, Liu Y, He J, et al. Large scale synthesis of manganese oxide/reduced graphene oxide composites as anode materials for long cycle lithium ion batteries. *ACS Appl Energy Mater*, 2021, 4: 5424–5433
- Park J H, Choi W Y, Lee S, et al. Graphene intercalated free-standing carbon paper coated with MnO₂ for anode materials of lithium ion batteries. *Electrochim Acta*, 2020, 348: 136310
- Zhang M, Jin D, Zhang L, et al. High energy storage MnO₂@C fabricated by ultrasonic-assisted stepwise electrodeposition and vapor carbon coating. *Chem Eng J Adv*, 2021, 6: 100098
- Zeng H, Xing B, Zhang C, et al. *In situ* synthesis of MnO₂/porous graphitic carbon composites as high-capacity anode materials for lithium-ion batteries. *Energy Fuels*, 2020, 34: 2480–2491
- Abdollahi A, Abnavi A, Ghasemi F, et al. Facile synthesis and simulation of MnO₂ nanoflakes on vertically aligned carbon nanotubes, as a high-performance electrode for Li-ion battery and supercapacitor. *Electrochim Acta*, 2021, 390: 138826
- Song J, Li Y, Tong R, et al. Mn₂O₃ embedded within CNT supporting porous carbon for enhanced lithium storage. *J Phys Chem Solids*, 2022, 160: 110317
- Wang Z, Yan X, Wang F, et al. Reduced graphene oxide thin layer induced lattice distortion in high crystalline MnO₂ nanowires for high-performance sodium- and potassium-ion batteries and capacitors. *Carbon*, 2021, 174: 556–566
- Xing B, Zhang C, Liu Q, et al. Green synthesis of porous graphitic carbons from coal tar pitch templated by nano-CaCO₃ for high-performance lithium-ion batteries. *J Alloys Compd*, 2019, 795: 91–102
- Li Y, Liu X, Liu L, et al. Coal tar electrode pitch modified rice husk ash as anode for lithium ion batteries. *J Electrochem Soc*, 2019, 166: A2425–A2430
- Chen J, Yang K, Wang J, et al. Peanut-like yolk/core-shell MnO/C microspheres for improved lithium storage and the formation mechanism of MnCO₃ precursors. *J Alloys Compd*, 2020, 849: 156637
- Park S K, Jin A, Yu S H, et al. *In situ* hydrothermal synthesis of Mn₃O₄ nanoparticles on nitrogen-doped graphene as high-Performance anode materials for lithium ion batteries. *Electrochim Acta*, 2014, 120: 452–459
- Bourlinos A B, Gournis D, Petridis D, et al. Graphite oxide: Chemical reduction to graphite and surface modification with primary aliphatic amines and amino acids. *Langmuir*, 2003, 19: 6050–6055
- Szabó T, Berkesi O, Forgó P, et al. Evolution of surface functional groups in a series of progressively oxidized graphite oxides. *Chem Mater*, 2006, 18: 2740–2749
- Wang K, Ju D Y, Xu G Y, et al. Organosilicon modified method to improve Li⁺ storage capacity of graphene oxide (GO). *Sci China Tech Sci*, 2020, 63: 2709–2716
- Zhang W, Xu H, Xie F, et al. General synthesis of ultrafine metal oxide/reduced graphene oxide nanocomposites for ultrahigh-flux nanofiltration membrane. *Nat Commun*, 2022, 13: 471–480
- Jia H N, Lin J H, Liu Y L, et al. Nanosized core-shell structured graphene-MnO₂ nanosheet arrays as stable electrodes for superior supercapacitors. *J Mater Chem A*, 2017, 5: 10678–10686
- Kim I G, Ghani F, Lee K, et al. Electrochemical performance of Mn₃O₄ nanorods by N-doped reduced graphene oxide using ultrasonic spray pyrolysis for lithium storage. *Int J Energy Res*, 2020, 44: 11171–11184
- Ang Z W J, Xiong T, Lee W S V, et al. Oxygen-deficient birnessite-MnO₂ for high-performing rechargeable aqueous zinc-ion batteries. *ChemNanoMat*, 2020, 6: 1357–1364
- Cai Y, Chua R, Huang S, et al. Amorphous manganese dioxide with the enhanced pseudocapacitive performance for aqueous rechargeable zinc-ion battery. *Chem Eng J*, 2020, 396: 125221
- Wang J, Zhang C, Kang F. Nitrogen-enriched porous carbon coating for manganese oxide nanostructures toward high-performance lithium-ion batteries. *ACS Appl Mater Interfaces*, 2015, 7: 9185–9194
- Ao L, Wu C, Xu Y, et al. A novel Sn particles coated composite of SnO/ZnO and N-doped carbon nanofibers as high-capacity and cycle-stable anode for lithium-ion batteries. *J Alloys Compd*, 2020, 819: 153036
- Huang S Z, Cai Y, Jin J, et al. Unique walnut-shaped porous MnO₂/C nanospheres with enhanced reaction kinetics for lithium storage with high capacity and superior rate capability. *J Mater Chem A*, 2016, 4: 4264–4272
- Li Z, Cai L, Chu K, et al. Heteroatom-doped carbon materials with interconnected channels as ultrastable anodes for lithium/sodium ion batteries. *Dalton Trans*, 2021, 50: 4335–4344
- Schilling C, Hofmann A, Hess C, et al. Raman spectra of polycrystalline CeO₂: A density functional theory study. *J Phys Chem C*, 2017, 121: 20834–20849
- Hattori T, Kobayashi K, Ozawa M. Size effect of Raman scattering on CeO₂ nanocrystal by hydrothermal method. *Jpn J Appl Phys*, 2017, 56: 01AE06
- Deng Z, Huang X, Zhao X, et al. Facile synthesis of hierarchically structured manganese oxides as anode for lithium-ion batteries. *J Cent South Univ*, 2019, 26: 1481–1492
- Wan H, Ju X, He T, et al. Sulfur-doped porous carbon as high-capacity

- anodes for lithium and sodium ions batteries. *J Alloys Compd*, 2021, 863: 158078
- 38 Wei F, Zhang H, He X, et al. Synthesis of porous carbons from coal tar pitch for high-performance supercapacitors. *New Carbon Mater*, 2019, 34: 132–139
- 39 Luo J, Hu W, Suo Z, et al. Co-pyrolysis of spent radioactive ion exchange resin and manganese dioxide: Decrease the decomposition temperatures of functional groups. *J Hazard Mater*, 2021, 418: 126275
- 40 Zhong S, Zhang H, Fu J, et al. *In-situ* synthesis of 3D carbon coated zinc-cobalt bimetallic oxide networks as anode in lithium-ion batteries. *ChemElectroChem*, 2018, 5: 1708–1716
- 41 Vijayan B L, Misnon I I, Anil Kumar G M, et al. Facile fabrication of thin metal oxide films on porous carbon for high density charge storage. *J Colloid Interface Sci*, 2020, 562: 567–577
- 42 Moon S, Kim D H, Kwak J H, et al. Unveiling the pseudocapacitive effects of ultramesopores on nanoporous carbon. *Appl Surf Sci*, 2021, 537: 148037
- 43 Jia Y, Yang Z, Li H, et al. Reduced graphene oxide encapsulated MnO microspheres as an anode for high-rate lithium ion capacitors. *New Carbon Mater*, 2021, 36: 573–584
- 44 Oh S M, Kim I Y, Adpakpang K, et al. The beneficial effect of nanocrystalline and amorphous nature on the anode performance of manganese oxide for lithium ion batteries. *Electrochim Acta*, 2015, 174: 391–399
- 45 Wu H, Zhou S, Tseng C, et al. One-pot solution combustion synthesis of crystalline and amorphous molybdenum trioxide as anode for lithium-ion battery. *J Am Ceram Soc*, 2020, 104: 1102–1109
- 46 Wu Y, Fee J, Tobin Z, et al. Amorphous manganese oxides: An approach for reversible aqueous zinc-ion batteries. *ACS Appl Energy Mater*, 2020, 3: 1627–1633
- 47 Chen M, Liu J, Chao D, et al. Porous α -Fe₂O₃ nanorods supported on carbon nanotubes-graphene foam as superior anode for lithium ion batteries. *Nano Energy*, 2014, 9: 364–372
- 48 Jadhav H S, Rai A K, Lee J Y, et al. Enhanced electrochemical performance of flower-like Co₃O₄ as an anode material for high performance lithium-ion batteries. *Electrochim Acta*, 2014, 146: 270–277
- 49 Jia B, Chen W, Luo J, et al. Construction of MnO₂ artificial leaf with atomic thickness as highly stable battery anodes. *Adv Mater*, 2020, 32: 1906582
- 50 Gogotsi Y, Penner R M. Energy storage in nanomaterials-capacitive, pseudocapacitive, or battery-like? *ACS Nano*, 2018, 12: 2081–2083
- 51 Choi C, Ashby D S, Butts D M, et al. Achieving high energy density and high power density with pseudocapacitive materials. *Nat Rev Mater*, 2020, 5: 5–19
- 52 Wang X, Liu J, Hu Y, et al. Oxygen vacancy-expedited ion diffusivity in transition-metal oxides for high-performance lithium-ion batteries. *Sci China Mater*, 2022, 65: 1421–1430
- 53 Fang G, Wu Z, Zhou J, et al. Observation of pseudocapacitive effect and fast ion diffusion in bimetallic sulfides as an advanced sodium-ion battery anode. *Adv Energy Mater*, 2018, 8: 1703155
- 54 Wang Y, Liu H, Wang K, et al. Synthesis and electrochemical performance of nano-sized Li₄Ti₅O₁₂ with double surface modification of Ti(III) and carbon. *J Mater Chem*, 2009, 19: 6789–6795
- 55 Zhu K, Wang X, Liu J, et al. Novel amorphous MoS₂/MoO₃/nitrogen-doped carbon composite with excellent electrochemical performance for lithium ion batteries and sodium ion batteries. *ACS Sustain Chem Eng*, 2017, 5: 8025–8034
- 56 Zhang Y, Chen P, Wang Q, et al. High-capacity and kinetically accelerated lithium storage in MoO₃ enabled by oxygen vacancies and heterostructure. *Adv Energy Mater*, 2021, 11: 2101712